arXiv:1211.4203v1 [cond-mat.str-el] 18 Nov 2012

Microscopic Coexistence of Antiferromagnetic and Spin-Glass States

Sh. Chillal,[1] M. Thede,[1] F.J. Litterst,[2] S.N. Gvasaliya,[1, *] T.A. Shaplygina,[3] S.G. Lushnikov,[3] and A. Zheludev[1, †]
[1] *Neutron Scattering and Magnetism, Laboratory for Solid State Physics, ETH Zürich, Zürich, Switzerland*
[2] *Institut für Physik der Kondensierten Materie, Technische Universität Braunschweig, 38106 Braunschweig, Germany*
[3] *Ioffe Physico-Technical Institute RAS, 194021, St. Petersburg, Russia*

(Dated: November 20, 2012)

The disordered antiferromagnet $PbFe_{1/2}Nb_{1/2}O_3$ (PFN) is investigated in a wide temperature range by combining Mössbauer spectroscopy and neutron diffraction experiments. It is demonstrated that the magnetic ground state is a *microscopic* coexistence of antiferromagnetic and a spin-glass orders. This speromagnet-like phase features frozen-in short-range fluctuations of the Fe^{3+} magnetic moments that are transverse to the long-range ordered antiferromagnetic spin component.

Phase transitions in the presence of disorder and/or competing interactions are one of the central unresolved problems in modern condensed matter physics [1–3]. With both effects present, one may encounter a freezing of microscopic degrees of freedom without conventional long-range order. In magnetic systems, the corresponding phenomenon is referred to as a spin-glass (SG) transition [4]. By now, spin glasses are reasonably well understood for models with discrete (Ising) symmetries and long-range interactions [5, 6]. In contrast, for continuous (Heisenberg and XY) symmetries with short-range coupling, the properties and sometimes the very existence of the SG phase remain a matter of debate [7–11]. In particular, precious little is known on whether in such systems a SG phase can coexist with true long-range order [11, 12].

Attempts to resolve these issues through numerical simulations of continuous models have met mixed success [10, 11], due to a progressively degrading calculation precision in the immediate vicinity of the freezing temperature T_{SG}. On the other hand, experiments face their own unique challenges [1, 13, 14]. Momentum-resolved (scattering) techniques are well-suited to probe microscopic quantities averaged over the entire sample, such as propagation vectors of emerging periodic structures and coherence scales. Their main drawback is their inability to distinguish a true microscopic coexistence of two types of ordering from simple phase separation [1]. In contrast to these, local-probe resonant methods have excellent sensitivity to local environments. They are ideal tools for validating homogeneity on the microscopic level, but carry no information on spatial coherence. It is only by combining the two approaches that the coexistence of complex phases can be unambiguously established. In this Letter we report combined Mössbauer spectroscopy and neutron scattering experiments on the disordered antiferromagnet $PbFe_{1/2}Nb_{1/2}O_3$. We prove that in this Heisenberg system a *spin-glass state and true antiferromagnetic long-range order coexist on the microscopic scale.*

Our target material, abbreviated PFN , is a well-known complex perovskite. Its structure is shown in Fig. 1 (left panel). The Pb ions reside at the corners of the unit cell, while oxygen octahedra surrounds the Fe and Nb sites. The material is nearly cubic with a lattice constant $a = 4.01$ Å [15]. The magnetic Fe^{3+} and non-magnetic Nb^{5+} are randomly distributed over the B-sites of the perovskite lattice [15, 16]. AF long-range order occurs below $T_N \sim 145$ K. The Fe^{3+} moments are arranged in a simple *G*-type structure [17] as shown by blue arrows in the right panel of Fig. 1. The spin glass state emerges at a lower temperature, $T_{SG} \sim 12$ K. It is manifested in a difference between magnetization curves measured in zero-field-cooled (ZFC) and field-cooled samples [18]. What is known from combined muon-spin rotation (μSR) and neutron scattering studies, is that the long-range AF order in PFN is not destroyed by the appearance of SG state [19]. However, based on the magnetoelectric (ME) experiments, it has been argued that this coexistence is a phase separation[20]. In this model, the two type of order emerge independently on separate subsystems: infinite-range percolation cluster (AF) and isolated Fe^{3+} ions and unblocked superantiferromagnetic Fe^{3+} clusters (SG). Below we shall demonstrate that, in fact, the coexistence is a single homogeneous phase, with the magnetic moments arranged in a speromagnetic-like fashion, as indicated by the red arrows in the right panel of Fig 1b.

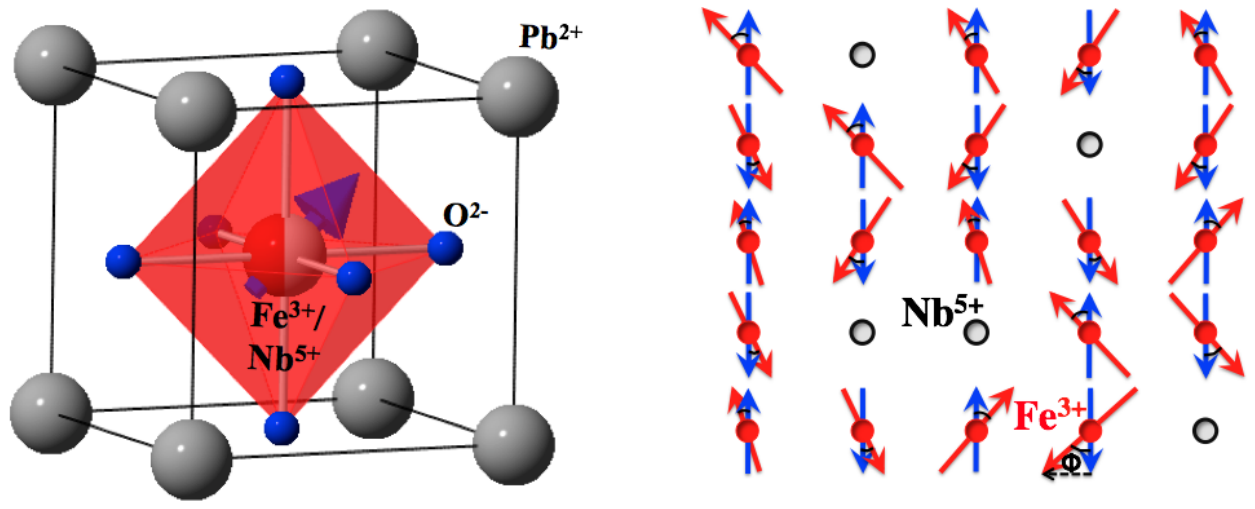

FIG. 1: Left: Structural motif of $PbFe_{1/2}Nb_{1/2}O_3$. Right: Antiferromagnetic G-type order of Fe^{3+} moments in the collinear phase (blue arrows) and proposed model for speromagnetic-like ordering in the antiferromagnetic spin glass phase (red arrows). The tilt angle Φ randomly varies from site to site averaging to zero. Nb^{5+} are non-magnetic.

In our PFN samples [21], the two phase transitions

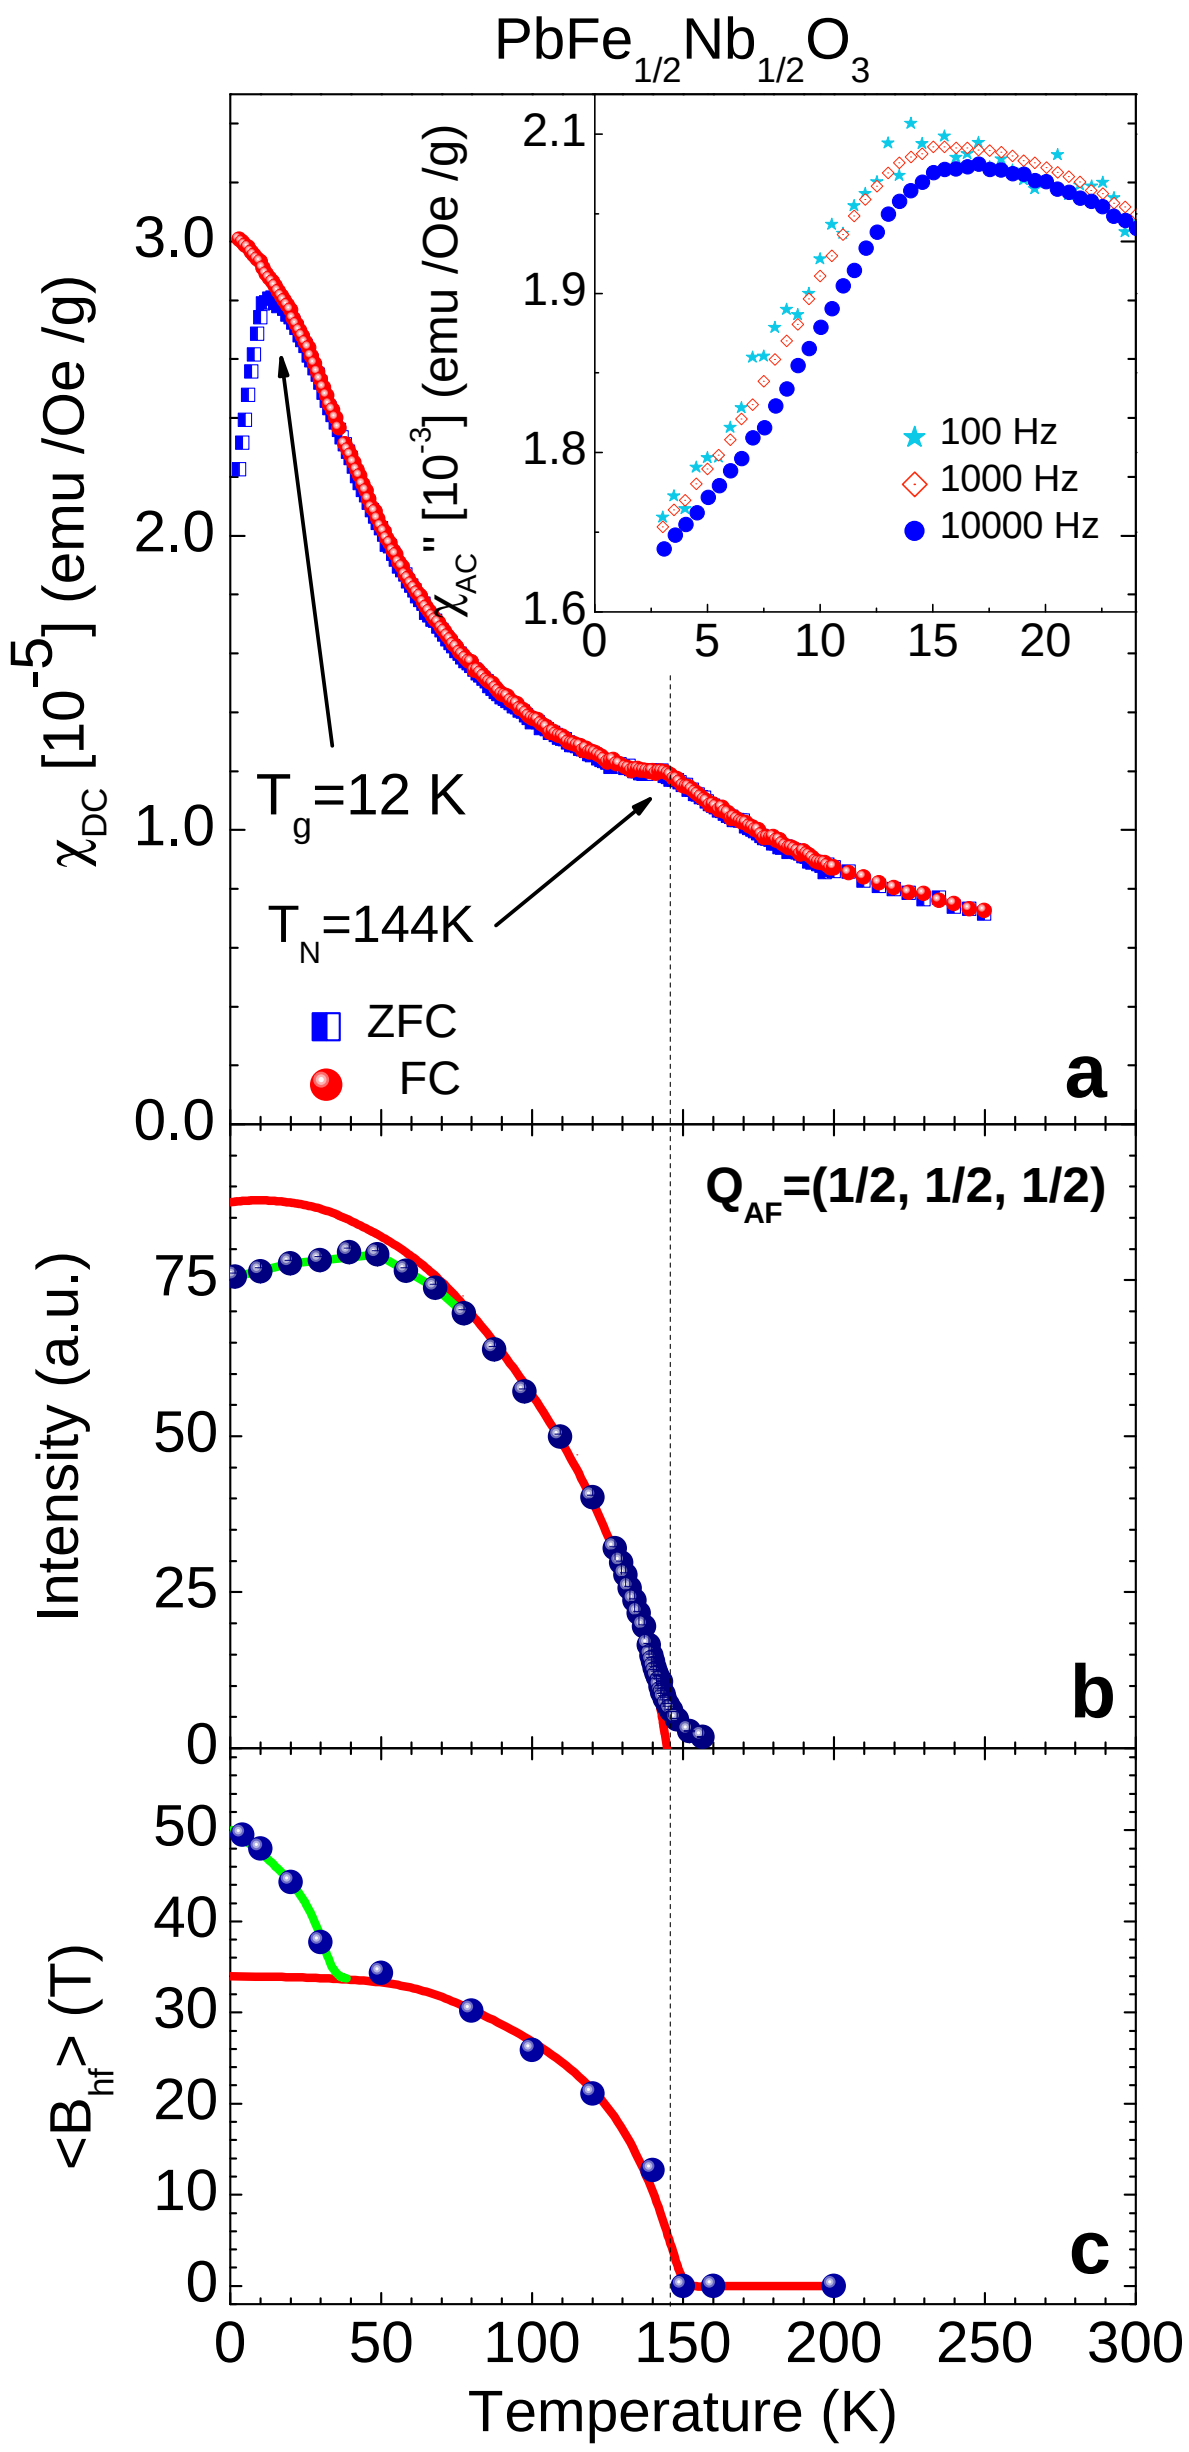

FIG. 2: (a) DC susceptibility of PFN taken measured in 500 Oe applied field following ZFC and FC protocols. Inset: AC-susceptibility taken in the range 10^2 - 10^4 Hz (b) Measured temperature dependence of the intensity of an antiferromagnetic Bragg peak in PFN (symbols). (c) Average hyperfine field $\langle B_{hf} \rangle$ obtained from the Mössabuer spectra as a function of temperature. All lines are guides for the eye.

are readily observed in macroscopic experiments. Figure 2a shows magnetic DC susceptibility versus temperature obtained using ZFC and FC protocols [24]. Below $T_{\rm SG} \sim 12$ K the two curves diverge as is typical for a spin glass. SG behavior is further evidenced by the gradual frequency dependence of the rounded peak in AC susceptibility (Figure 2a, inset). In contrast, the small cusp in susceptibility which is due to AF ordering at $T_{\rm N}$ does not show noticeable history effects. These observations are in agreement with previous reports [18, 20, 23]. Of course, as any true long range ordering, the AF phase transition is best represented by the emergence of a new AF Bragg peak in neutron diffraction. The measured temperature dependence of the $\mathbf{Q} = (1/2, 1/2, 1/2)$ Bragg intensity is plotted in Figure 2b [25]. As expected for an AF, the intensity of the magnetic Bragg peak (*i.e.* square of magnetization) increases smoothly below $\rm T_N$.

Verifying the coexistence of the SG and AF phases the microscopic level calls for the use of microscopic local probes. For this purpose Mössbauer spectroscopy employs magnetic nuclei already present in the material, in our case those of ^{57}Fe. In a paramagnetic state, the position of the nuclear absorption line is the isomer (chemical) shift, related to the valence state of the ion. This line may exhibit additional quadrupolar splitting due to a non-spherical charge distribution around the ion, resulting in an electric field gradient at the nuclear site. In magnetically ordered phases, the degeneracy of the nuclear energy levels is further lifted by the local hyperfine field at the nuclei, generated by the static sublattice magnetization. The resulting energy intervals between the lines are then a measure of the iron magnetic moment.

The way this scenario plays out in $\rm PbFe_{1/2}Nb_{1/2}O_3$ is illustrated by the typical Mössbauer spectra shown in Fig. 3 [26]. All data were collected on powder samples prepared by grinding either single crystals or ceramic material, with virtually identical results. At T=200 K, in the paramagnetic phase, a single structured line is observed (Fig. 3a). The additional slight splitting is due to the above-mentioned quadrupolar effect [27]. For all samples studied in this work, the spectra measured at $T > T_{\rm N}$ can be fit (red line in Fig. 3) assuming two types of $\rm Fe^{3+}$ sites with distinct isomer shifts (blue and green line). As discussed elsewhere [27], the two different sites may correspond to local variations in chemical short range order. Our analysis yields approximately equal populations for the two components [28] . The obtained isomer shifts can be unambiguously attributed to trivalent high spin iron $\rm Fe^{3+}$.

Below $T_{\rm N}$, the single line is split due to the appearance of long range order, as shown in Figs. 3 b–d. The temperature dependence of the measured average hyperfine field $\langle B_{hf} \rangle$ is presented in Fig. 2c. In the AF phase, it follows the magnetic order parameter, as expected. However, a crucial new observation is that the unsplit component that dominated in the paramagnetic state, is no longer present below $T_{\rm N}$. This immediately rules out the phase separation model of Ref. [20]. In the latter, the low temperature SG phase is confined to isolated spin clusters. Above $T_{\rm SG}$ these would simply be paramagnetic, and necessarily produce an magnetically unsplit resonance line. In contrast, our data show that *all spins in the system are involved in the AF order.* At the same time we note

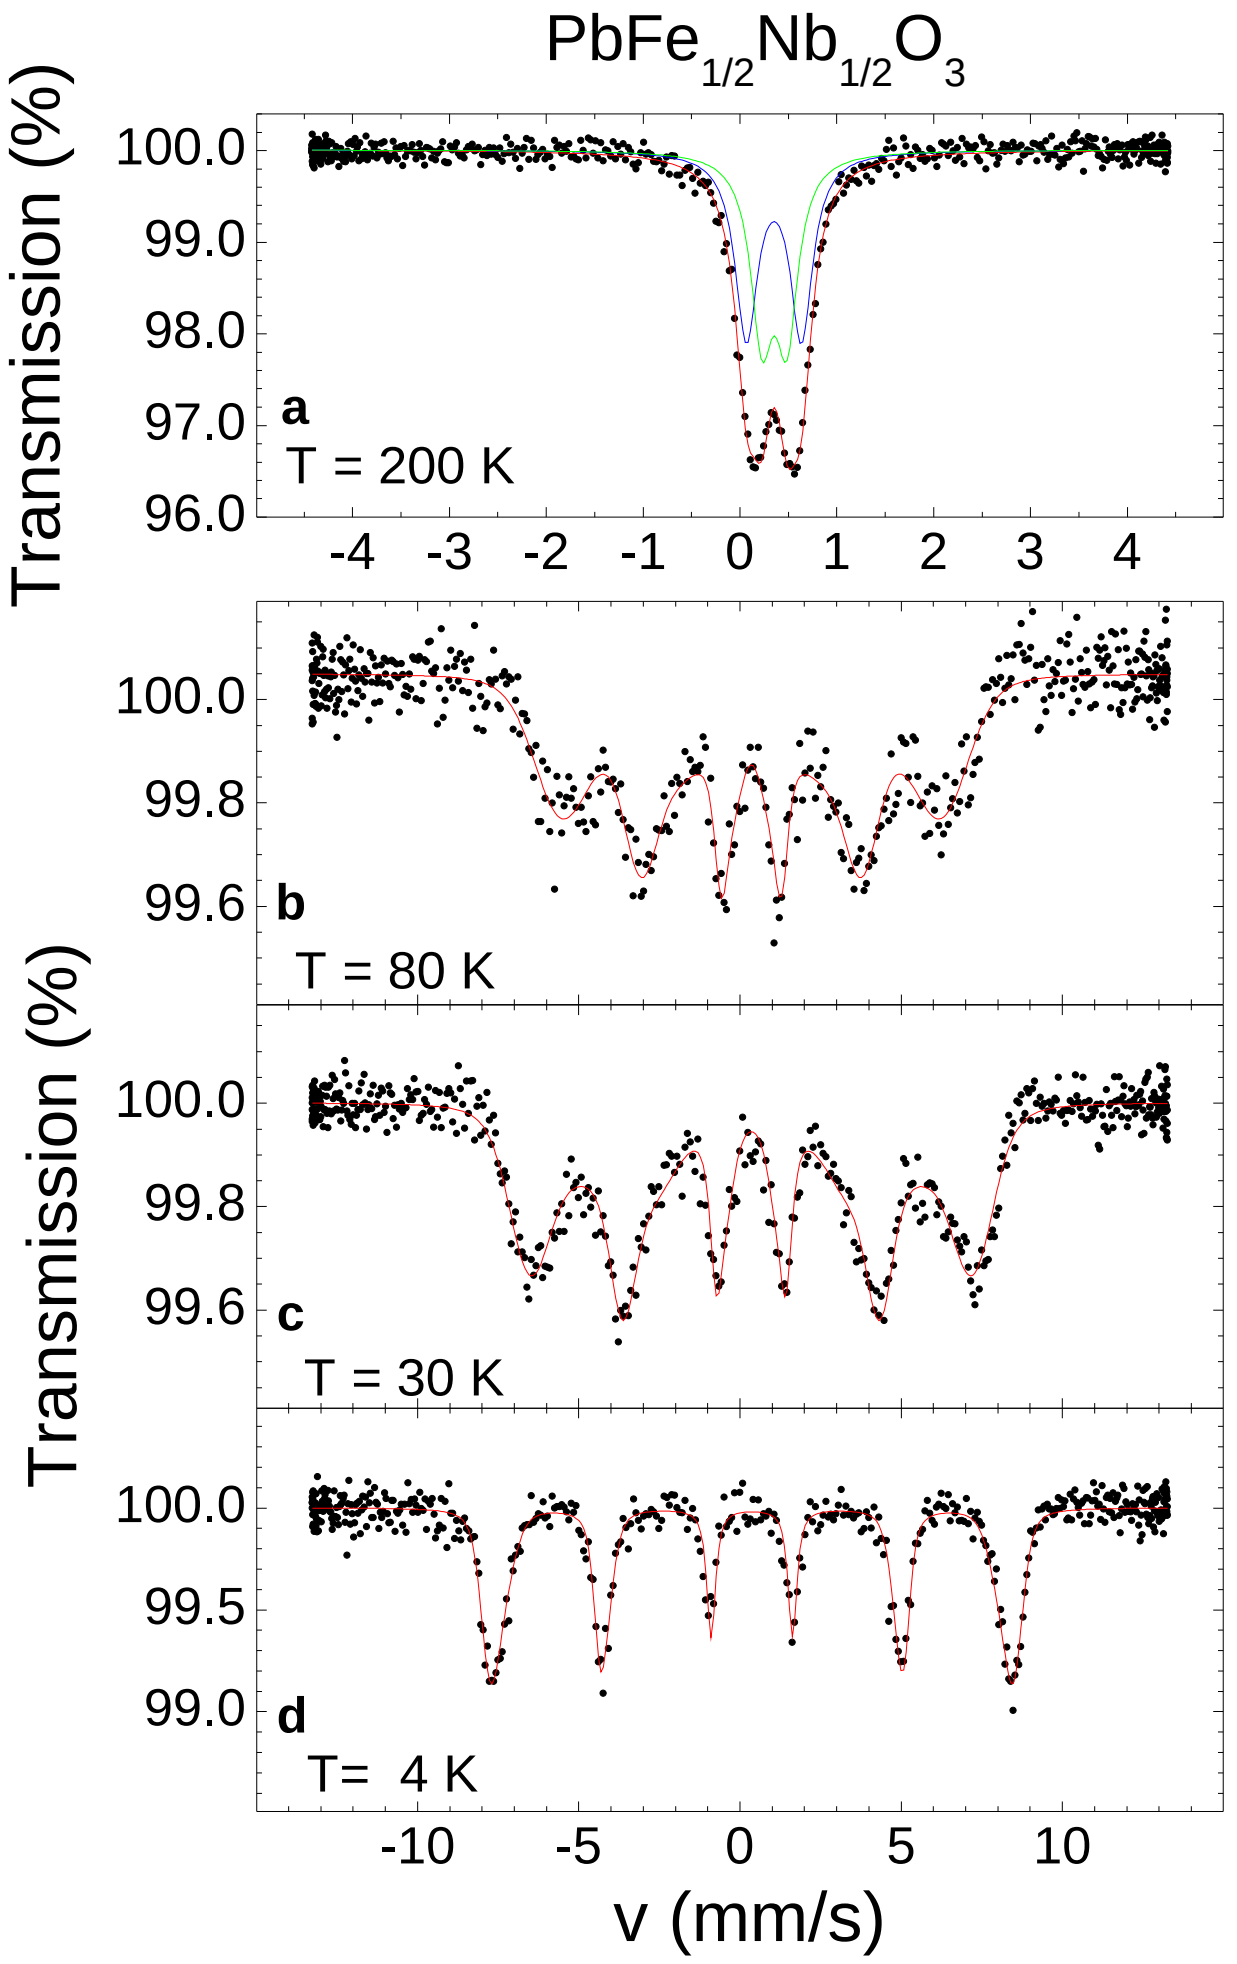

FIG. 3: Representative Mössbauer spectra of PFN taken in the paramagnetic phase (a) and below its Néel temperature (b-d). Note a reduced velocity scale in panel (a).

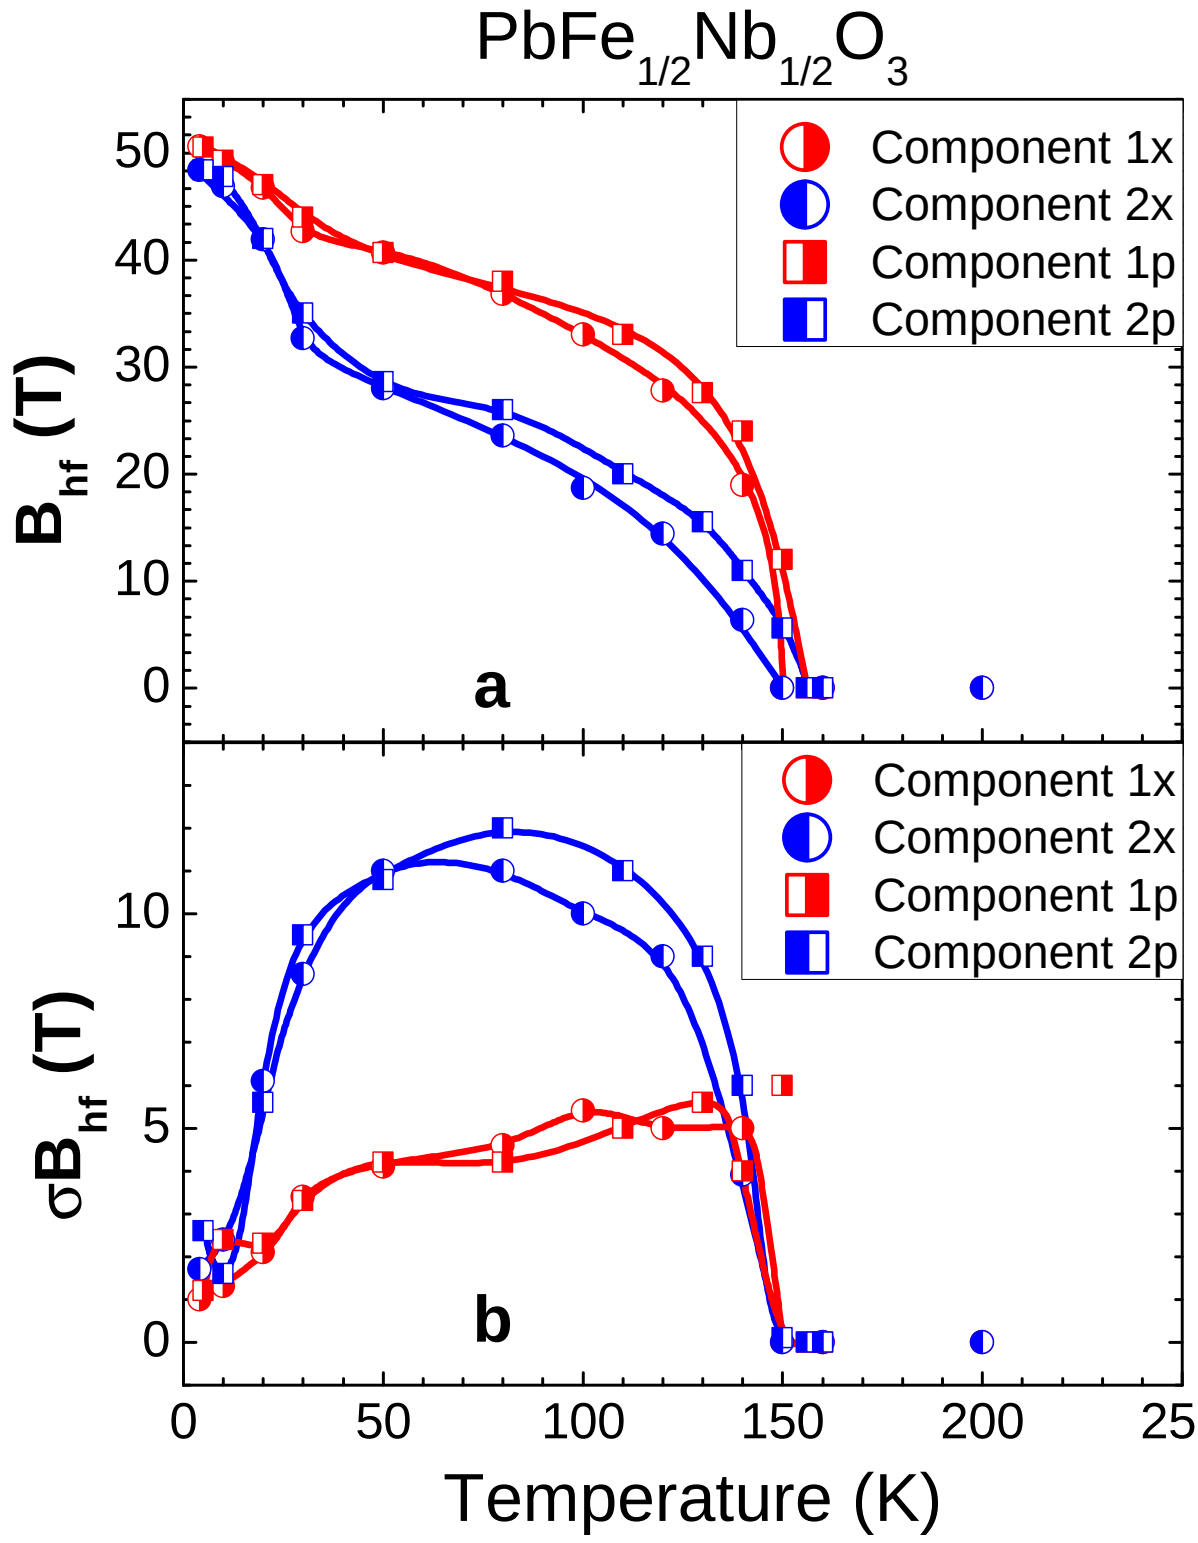

FIG. 4: The magnetic hyperfine fields for the two Fe^{3+} sites (1,2) as deduced from the measured Mössabuer spectra, as described in the text. Labels "c" and "x" stand for ceramic and crystalline samples, respectively.

that the quadrupolar splitting, so clearly visible at high temperatures, is absent below $T_{\rm N}$. This indicates a wide distribution of angles between the iron spin and the local axes of the electric field gradient tensor.

Important clues to the nature of the ordered phases are obtained by a more thorough quantitative analysis [27, 29]. The simplest strategy is to treat the spectra as superpositions of two contributions with distinct hyperfine fields. Even so, to obtain a good fit, one has to allow for an intrinsic and temperature-dependent broadening of the absorption lines, which implies a *distribution of magnetic hyperfine fields*. Assuming these distributions to be Gaussian, and fitting the data to the resulting model, produces the fits shown in red lines in Figs. 3 b–d. The procedure consistently yields equal spectral weights of the two components at all temperatures. The hyperfine fields for each one are separately plotted as a function of temperature in Fig. 4a.

Another experimental result that firmly supports a microscopic coexistence of AF and SG orders is the measured temperature dependence of the width σB_{hf} of the hyperfine field distribution (Fig. 4b). For both sites, σB_{hf} gradually increases on cooling below $T_{\rm N}$ in the AF phase and reaches a broad maximum between 120 K and 50 K. Below $T \sim 50$ K, the distribution width decreases drastically, and remains very small and constant below $T_{\rm SG}$ ~12K. The most natural interpretation of such behavior is that line broadening is due to slow fluctuations of local magnetic fields within Mössbauer frequency window (MHz to GHz). In this context, the narrowing of the lines at low temperatures indicates that *the very same spins that were fluctuating the the AF state, become frozen in the SG phase.* Such behavior is totally inconsistent with the above-mentioned inhomogeneous model. A separation into smaller dynamic clusters and infinitely connected static AF cluster would result in narrower lines in the high temperature AF phase, where only the latter are present.

That the magnetic state below about 10K is homogeneous as sensed by the Mössbauer nuclei, is also supported by the nearly coinciding saturation values of B_{hf} for the two contributions with distinct isomer shifts. These value are close to an average hyperfine field at saturation typically found in other Fe^{3+}-based perovskites

[33], suggesting a full recovery of the Fe^{3+} moment at the lowest temperature.

We are now in a position to propose a model for the low-temperature magnetic structure of PFN. As mentioned, the variation of B_{hf} above 50 K (Fig. 2c) roughly follows that of the AF long range order parameter determined by neutron diffraction (Fig. 2b). It stands to reason that in this regime it mainly reflects the evolution of the collinear long range ordered AF component $\langle S^z(T)\rangle$ of Fe^{3+} (Fig. 1b, blue arrows). The increase of mean magnetic hyperfine fields on cooling below 50 K (Fig. 2c, green line), is reminiscent of precursor phenomena in ferromagnetic re-entrant spin-glass systems like AuFe [30, 31] or the mixed spinel $Mg_{1+t}Fe_{2-2t}Ti_tO_4$ [32]. It represents a gradual freezing of transverse spin components within Mössbauer frequency window. In other words, there occurs a tilting of the ionic moments from the z direction set by the AF long-range order (Fig. 1b, red arrows). The process culminates in a complete (static) freezing at T_{SG}. From the change of B_{hf} observed between 50 K and 4 K, we can roughly estimate the typical tilt angles to be $\sim 30^o$ and $\sim 55^o$.

Unlike the longitudinal component, the transverse one show no long-range correlations. For this reason, it contributes nothing to the AF Bragg peak intensity, and is, in fact be liable for the reduction of the latter observed at low temperatures (Fig. 2b, green line). On the other hand, it contributes to the diffuse neutron magnetic scattering, previously observed in PFN [19].

In conclusion, at low temperatures, the Heisenberg system $PbFe_{1/2}Nb_{1/2}O_3$ realizes a unique combination of antiferromagnetic long range order for one set of spin components, and a spin glass state for the transverse ones.

This work is partially supported by the Swiss National Fund through MANEP.

---

[*] sgvasali@phys.ethz.ch

[†] zhelud@ethz.ch; `http://www.neutron.ethz.ch/`

[1] E. Dagotto, Science **309**, 257 (2005).

[2] D. Bergman, J. Alicea, E. Gull, S. Trebst, L. Balents, Nature Phys. **3**, 487 (2007).

[3] R.G. Palmer, D. Stein, E.S. Abrahams, P.W. Anderson, Phys. Rev. Lett. **53**, 958 (1984).

[4] K. Binder, A.P. Young, Rev. Mod. Phys. **58**, 801 (1986).

[5] M. Palassini and S. Caracciolo, Phys. Rev. Lett. **82**, 5128 (1999).

[6] H.G. Ballesteros, A. Cruz, L.A. Fernandez, V. Martin-Mayor, J. Pech, J.J. Ruiz-Lorenzo, A. Tarancon, P. Tellez, C. L. Ullod, and C. Ungil, Phys. Rev. B **62**, 14237 (2000).

[7] S. Abiko, S. Niidera, and F. Matsubara, Phys. Rev. Lett. **94**, 227202 (2005)

[8] L.W. Lee and A.P. Young, Phys. Rev. Lett. **90**, 227203 (2003).

[9] D.-X. Viet and H. Kawamura, Phys. Rev. Lett. **102**, 027202 (2009).

[10] D.-X. Viet and H. Kawamura, Phys. Rev. Lett. **105**, 097206 (2010).

[11] A.P. Young, Journal of Physics: Conference Series **95**, 012003 (2008).

[12] K. Binder, W. Kob "Glassy Materials and Disordered Solids, 2nd revised edition (World Scientific, Singapore, 2011).

[13] E. Dagotto, T. Hotta, and A Moreo, Phys. Rep. **344**, 1 (2001).

[14] D.C. Johnston Adv. in Phys. **59**, 803 (2010).

[15] V. Bonny, M. Bonin, Ph. Sciau, K.J. Schenk, and G. Chapuis, Solid State Comm. **102**, 347 (1997).

[16] C.N.W. Darlington, J. Phys.: Condens. Matter **3**, 4173 (1991).

[17] S.A. Ivanov, R. Tellgren, H. kan Rundlof, N.W. Thomas, S. Ananta, J. Phys.: Condens. Matter **12**, 2393 (2000).

[18] A. Falqui, N. Lampis, A. Geddo-Lehmann, and G. Pinna, J. Phys. Chem. B **109**, 22967 (2005).

[19] G.-M. Rotaru, B. Roessli, A. Amato, S. N. Gvasaliya, S. G. Lushnikov, T. A. Shaplygina, Phys. Rev. B **79**, 184430 (2009).

[20] W. Kleemann, V.V. Shvartsman, P. Borisov, and A. Kania, Phys. Rev. Lett. **105**, 257202 (2010).

[21] PFN ceramics were sintered using the conventional two-stage technology described *e.g.* in [22]. Single crystals were prepared using the spontaneous crystallization technique as described in Ref. [23].

[22] S.N. Gvasaliya, S.G. Lushnikov, I.L. Sashin, T.A. Shaplygina, J. Appl. Phys. **94**, 1130 (2003)

[23] A. Kumar, R.S. Katiyar, C. Rinaldi, S.G. Lushnikov, and T.A. Shaplygina, Appl. Phys. Lett. **93**, 232902 (2008).

[24] Magnetization and susceptibility measurements were performed using a PPMS from Quantum Design.

[25] Neutron scattering experiments were performed on a single crystal sample at the TASP 3-axis cold neutron spectrometer at Paul Scherrer Institut, using $k = 2.662\text{Å}^{-1}$ neutrons. Sample environment was a standard "orange" cryostat.

[26] Conventional ^{57}Fe Mössbauer absorption spectroscopy experiments in transmission geometry we performed on 60 mg/cm^2 powder samples, which corresponds to 0.1 mg/cm^2 of ^{57}Fe. The absorbers were kept within nylon containers in a static helium exchange gas atmosphere of about 0.2 mbar in a liquid helium flow cryostat.

[27] I.P. Raevski, S.P. Kubrin, S.I. Raevskaya, D.A. Sarychev, S.A. Prosandeev,M.A. Malitskaya, Phys. Rev. B **85**, 224412 (2012).

[28] Ref. [27] reports a ratio 0.78 : 0.22.

[29] Y. Yang, J.-M. Liu, H. B. Huang, W. Q. Zou, P. Bao, Z. G. Liu, Phys. Rev. B **70**, 132101 (2004).

[30] J. Lauer, W. Keune, Phys. Rev. B **48**, 1850 (1982).

[31] R.A. Brand, J. Lauer, W. Keune, Phys. Rev. B **31**, 1630 (1985).

[32] R.A. Brand, H. Georges-Gibert, J. Hubsch, J.A. Heller, J. Phys. F: Met. Phys. **15**, 1987 (1985).

[33] G. Shirane, D.E. Cox, and S. L. Ruby, Phys. Rev. **125**, 1158 (1962).